

Cite this: *Nanoscale*, 2018, **10**, 1135

# Metal ion assisted interface re-engineering of a ferritin nanocage for enhanced biofunctions and cancer therapy†

Zhantong Wang,<sup>‡a,b</sup> Yunlu Dai,<sup>‡a</sup> Zhe Wang,<sup>\*a</sup> Orit Jacobson,<sup>a</sup> Fuwu Zhang,<sup>a</sup> Bryant C. Yung,<sup>a</sup> Pengfei Zhang,<sup>b</sup> Haiyan Gao,<sup>b</sup> Gang Niu,<sup>a</sup> Gang Liu <sup>\*b</sup> and Xiaoyuan Chen <sup>\*a</sup>

The bottom-up self-assembly of protein subunits into supramolecular nanoarchitectures is ubiquitously exploited to recapitulate and expand the features of natural proteins to advance nanoscience in medicine. Various chemical and biological re-engineering approaches are available to render diverse functions in the given proteins. They are, unfortunately, capable of compromising protein integrity and stability after extensive modifications. In this study, we introduce a new protein re-engineering method, metal ion assisted interface re-engineering (MAIR), to serve as a robust and universal strategy to extend the functions of self-assembly proteins by boosting structural features to advance their diverse biomedical applications. In particular, the MAIR strategy was applied to a widely used natural protein, ferritin, as a model protein to coordinate with copper ions in its mutagenic artificial metal binding domain. Structure directed rational protein mutagenesis was carried out at the C2 interface amino acid residues of the ferritin subunit for metal ion coordination site optimization. Copper binding at the artificial binding pocket was highly specific over the other divalent ions present in physiological fluids, and the structurally embedded copper ion in turn strengthened the overall protein integrity and stability. In the presence of isotopic copper-64, the interface re-engineered ferritin worked as a chelator-free molecular nanoprobe with an extraordinarily high specific activity to allow PET imaging of tumors in live animals. We also found that the re-engineered ferritin coordinating with copper ions demonstrates high drug loading capacity of a widely used anti-cancer agent, doxorubicin (DOX), to achieve significant drug retention at the tumor site and enhance tumor regression for improved anti-cancer effects. The MAIR approach, thus, exploited the copper ion to facilitate efficient one-step labeling of mutant ferritin derivatives for simultaneous molecular imaging and drug delivery. The reported interface re-engineering strategy provides an unparalleled opportunity to expand protein biofunctions to serve as a new theranostic agent in cancer research.

Received 3rd November 2017,  
Accepted 3rd December 2017

DOI: 10.1039/c7nr08188j

rsc.li/nanoscale

## Introduction

The self-assembly of polypeptides or protein subunits into specific geometrical architectures has been extensively investigated.<sup>1</sup> A profound understanding of protein subunit self-assembly into symmetrical and stable supramolecules has led

to the discovery of noncovalent interactions of protein–protein interfaces,<sup>2,3</sup> and provides the basis for protein structure interrogation and manipulation.<sup>4,5</sup> Self-assembled proteins with unique properties such as high stability, mono-dispersity, good solubility, and ease of genetic and chemical manipulation possess high potential in biomedical applications.<sup>6–10</sup> Recent attempts to *de novo* design of protein subunits to self-assemble into nanocages/nanoparticles have utilized computer-aided protein programs to precisely predict folding interfaces for designer proteins to advance medicine and materials.<sup>6,11</sup> Nevertheless, such strategies require complicated processes and extensive expertise along with sophisticated computational modeling. Alternatively, re-engineering of available natural or synthetic protein subunits with designated features presents a simpler strategy. In addition, the widely accessible validated protein crystal structure information provides

<sup>a</sup>Laboratory of Molecular Imaging and Nanomedicine, National Institute of Biomedical Imaging and Bioengineering, National Institutes of Health, Bethesda, Maryland 20892, USA. E-mail: Shawn.chen@nih.gov, zhe.wang2@nih.gov

<sup>b</sup>State Key Laboratory of Molecular Vaccinology and Molecular Diagnostics & Center for Molecular Imaging and Translational Medicine, School of Public Health, Xiamen University, Xiamen 361102, China. E-mail: gangliu.cmitm@xmu.edu.cn

†Electronic supplementary information (ESI) available. See DOI: 10.1039/c7nr08188j

‡These authors contributed equally to this work.

rational guidance on the protein re-engineering processes. This increases the chances of success in protein re-engineering to meet specific purposes, and is more adaptable to wider research studies.

A myriad of re-engineered protein self-assemblies have found various applications. Protein subunits have evolved to self-assemble into nanocages accommodating therapeutic agents, such as oligonucleotides or drugs, for effective drug delivery.<sup>12–14</sup> Some protein assemblies support additional protein fusion to assemble into sophisticated architectures. The fusion of up to two copies of green fluorescent proteins to each unit of a rationally designed 60-unit protein icosahedron produced highly bright “standard candles” for fluorescence imaging.<sup>4</sup> The fusion of the viral hemagglutinin to ferritin elicited broad immunization response to H1N1 influenza virus.

Surface modification of assembled proteins also extends the utility of nanostructured proteins. The exterior surface re-engineering of a small heat shock protein nanocage was decorated with a tumor associated macrophage targeting peptide for the detection of atherosclerotic plaque lesions.<sup>15</sup> Likewise, a viral capsid with polymer modification on the surface modulated immunogenicity in animals.<sup>16</sup> Meanwhile, the re-engineering of interior surfaces of assembling proteins endows them with multiple active sites for the synthesis of inorganic nanoparticles,<sup>17</sup> or provides optimal conditions for use as a nanoreactor for catalytic reactions.<sup>18</sup>

The cumulative knowledge on protein self-assembly reveals that the interface of assembling subunits has a pivotal role in tuning protein self-assembly through noncovalent bonds and interactions. In expanding the scope of re-engineering for protein assembly, it has been proposed that the interface re-engineering of proteins provide subtle control of the entire protein self-assembly behavior and its functions while maintaining the original protein integrity.<sup>19,20</sup> Several research papers published by the Tezcan group reported zinc ion templated non-self-linking proteins forming dimers or supramolecular assemblies.<sup>21,22</sup> The Degradó group at the University of Pennsylvania also reported two different protein subunits assembling into a heterotetrameric four-helix bundle after making specific amino acid mutations.<sup>23</sup> An interface re-engineered protein ensemble could serve as a pH-dependent molecular switch,<sup>20</sup> or create a novel protein cube with interface re-engineering of two natural proteins.<sup>24</sup> The interface re-engineering of proteins is thus an attractive approach to develop new protein assemblies with novel functions.

In executing interface re-engineering, the interface of subunits usually has restricted space in which only selective small molecules or metal ions can be accommodated without altering protein integrity and overall dimensions. Small molecules usually have limited spatial binding capacities to multiple amino acids, and their interactions with amino acid residues could be attenuated by surrounding interference. In contrast, transition metal ions have high binding affinity to most amino acid side chains. The coordination forces between metal ions and amino acid side chains provide stronger interfacial interactions than hydrogen bonds and van de Waals forces,<sup>25</sup> which

would constitute the major driving forces in protein self-assembly. Moreover, metal ions compensate the associated entropy expense in the transition of a binary to a ternary system, and impose a geometrical constraint for overall protein assembly. By changing different metal ions with varying affinities to particular amino acids, the interface interactions can be precisely refined upon demand. Meanwhile, some small molecules, such as doxorubicin (DOX), is able to additionally couple with metal ions to form nanocomplexes, such as Cu(II)-DOX,<sup>26</sup> Zn(II)-DOX<sup>27</sup> and Fe(III)-DOX.<sup>28</sup> This unique feature between the anti-cancer drug and metal ions expand the scope of MIAR protein re-engineering approaches for simultaneous self-assembly, protein labelling and drug delivery.

Ferritin nanocages have been broadly explored in various fields.<sup>9,13,16</sup> In biomedicine, they have been used as delivery vehicles for effective anti-cancer drug delivery<sup>13,29</sup> or immunization vaccine against viruses.<sup>15</sup> Recent studies have reported the use of ferritins as effective nanoprobe for cancer diagnosis,<sup>24,30</sup> immunoassays,<sup>31</sup> and therapy.<sup>26</sup> Most of the applications rely heavily on chemical or biological modification of the original protein structure for desired properties. Such extensive uncontrolled refinement is likely to undermine protein integrity and functions. The substantial surface modification could lead to nanoparticle heterogeneity, structural instability, and batch to batch variation.

It is highly desirable to develop a simple one-step strategy to functionalize the ferritin nanocage as a theranostic agent for simultaneous bioimaging and drug delivery. In this study, we report a new protein interface re-engineering approach, MIAR, by using transition metal ions in conjunction with rational protein mutagenesis to refine self-assembly of the ferritin nanocage with enhanced physicochemical properties. The re-engineered nanocage is a new chelator-free molecular imaging nanoprobe with high specific radioactivity for positron emission tomography (PET) imaging of cancer. Meanwhile, such a nanocage chelating with Cu(II) improves doxorubicin loading capacity by multiple folds to ultimately broaden the therapeutic index for efficacious anti-cancer therapy. The new interface re-engineered approach revivifies the ferritin nanocage to serve as a quintessential example of a theranostic platform for chelator-free PET imaging and chemotherapy.

## Results and discussion


### Interface re-engineering of the ferritin nanocage

Ferritin is a spherical shell protein of about 460 kDa consisting of 24 identical subunits tightly packed in an octahedral symmetry with an inner diameter of 8 nm and an outer diameter of 12 nm.<sup>19,32</sup> The key step of interface re-engineering of ferritin is to search for the appropriate positions to install metal ion coordination motifs with low entropy cost in one of the symmetrical C2, C3 and C4 interfaces (Fig. S1†). The protein model in Fig. S1† shows that the C2 interface has a substan-

tially greater interacting surface area than C3 and C4 interfaces, and could be more amenable for structure re-engineering without compromising the protein's original integrity.<sup>19</sup> The amino acids that comprise the individual subunit of ferritin heavy chain fold into three long and one short alpha helix bundles, hence, the mutation sites along the interface of each alpha helix were carefully screened to accommodate Cu<sup>2+</sup> ions. It has been reported that the spatial configuration of Cu<sup>2+</sup> ion coordination with amino acids at the interface in the square planar format is favorable.<sup>33</sup> The introduction of two metal binding histidine residue mutants on each of the two adjacent subunits can meet the Cu<sup>2+</sup> coordination requirement to secure the neighboring subunits with high stability. A distance of two mutation sites in three amino acid intervals in each helix is required to secure Cu<sup>2+</sup> coordination at the interface. We used the ferritin protein crystal structure (PDB: 1FHA) to identify the entire interface sequences of a single ferritin heavy chain subunit, and rationally mutagenized specific amino acids into histidine residues having high binding affinity to a number of metal ions. We avoided the residues where alternations could potentially devastate the Naive configuration of the C2 interface, which has a dominant role in C3 and C4 interfaces,<sup>34</sup> and kept residues at the C2 interface core position unchanged to ensure the correct C2 interface alignment and formation.<sup>19</sup>

In expediting the mutation process, we employed a programmable stepwise cloning method circumventing the conventional site-directed mutation approach which is intricate and time-consuming. In our method, a total of 5 pairs of 60 mer DNA oligos were designed and synthesized, covering the entire span of ferritin subunit sequences with an appropriate length of overlapping in the two consecutive sequences (see the ESI† for details). Within five steps of regular PCR reactions, the designed mutation coding DNA sequences were synthesized (Fig. S2†), following a single step restriction enzyme digestion for complete expression plasmid construction. Table 1 shows the selected two optimal mutant (mutants A and B) amino acid residues, and a control mutant variant (mutant C) on the fourth alpha helix which results in no interaction with the two neighboring subunits. In selecting the appropriate residues as potential mutation sites, we kept the C2 interacting core residues and 2, 3 alpha helix loop residues unchanged, as subtle alterations on these sites could destabilize the subunit assembly and alignment in protein self-assembly.

It has been recently reported that residue pairs at sites 56 and 60 and sites 63 and 67 facing each other over the interface are appropriate positions to induce a mutation for symmetrical ion coordination in their initial screening.<sup>19</sup> This is consistent with our results on the high stability of mutant A protein in Cu<sup>2+</sup> coordination (Fig. 1). We conducted further mutation screening on residues in the same helix, and our results reveal that the residue pairs at sites 52 and 56 and sites 67 and 71 provide an optimal interface for Cu<sup>2+</sup> coordination (mutant B) (Fig. 1). The mutation pairs on the far end of the fourth helix present almost identical Cu<sup>2+</sup> binding affinity as that of native wild-type ferritin (Fig. 1C). Computational modeling is an important tool to facilitate the prediction of permuting protein structures and ion binding energy calculations. The calculated results (Fig. 1C and Table S1†) confirm that rational interface re-engineered ferritins (mutant A and B) have much higher Cu<sup>2+</sup> binding atoms and areas than those of the native ferritin, and the overall ferritin ensembles (mutant A and B) have enhanced stability with Cu<sup>2+</sup> binding at the assembly interface.

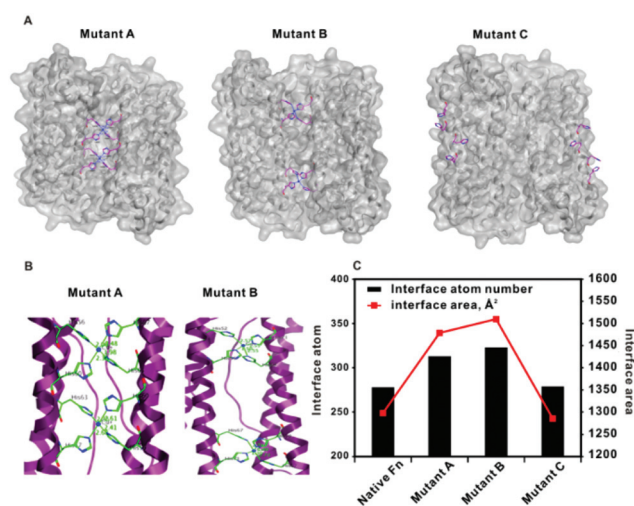

**Fig. 1** (A) Computational simulation of three interface re-engineered ferritin variants with copper chelation. (B) Magnified protein ribbon structures of two potent permuted ferritin variants coordinated with copper. The amino acid residues associated with copper coordination are labelled. (C) Computational calculation of the interface atom number and the interface area of different ferritin variants.

**Table 1** Amino acid sequences of native and mutative sites of ferritins


a.a. position	50	51	52	53	54	55	56	57	58	59	60	61	62	63	64	65	66	67	68	69	70	71	72	73
Native Fn	N	F	A	K	Y	F	L	H	Q	S	H	E	E	R	E	H	A	E	K	L	M	K	L	Q
Mutant A							H				H			H				H						
Mutant B			H				H											H				H		

a.a. position	137	138	139	140	141	142	143	144	145	146	147	148	149	150	151	152
Native Fn	Y	L	N	E	Q	V	K	S	I	K	E	L	G	D	H	V
Mutant C			H				H			H				H		

## Characterization of $\text{Cu}^{2+}$ coordination with interface re-engineered ferritin nanocages

Denaturing SDS-PAGE gel electrophoresis results showed that both the *E. coli* expressed and size-exclusion column purified ferritin subunit analogues presented identical molecular weight at 21 kDa with high purity (Fig. S3†). All re-engineered ferritin subunits can self-assemble into homogeneous spherical hollow nanocages as shown by TEM imaging (Fig. 2A), and both mutants A and B showed high stability in buffers of various pH values in the absence of  $\text{Cu}^{2+}$  ions (Fig. 2B). We further used circular dichroism (CD) spectroscopy to study the secondary structure of our targeted mutant B in PBS without  $\text{Cu}^{2+}$  ions (Fig. 2C). It was shown that mutant B had an identical secondary structure similar to native ferritin at physiological pH (pH = 7.2). Ferritin in general is a family of proteins that can tolerate a wide range of fusion peptide/protein modifications,<sup>24,35,36</sup> whereas the stability of the modified proteins is usually in question. Our results indicate that the interface re-engineered subunits retain the self-assembly feature for nanocage ensembles without compromising the secondary structural integrity.

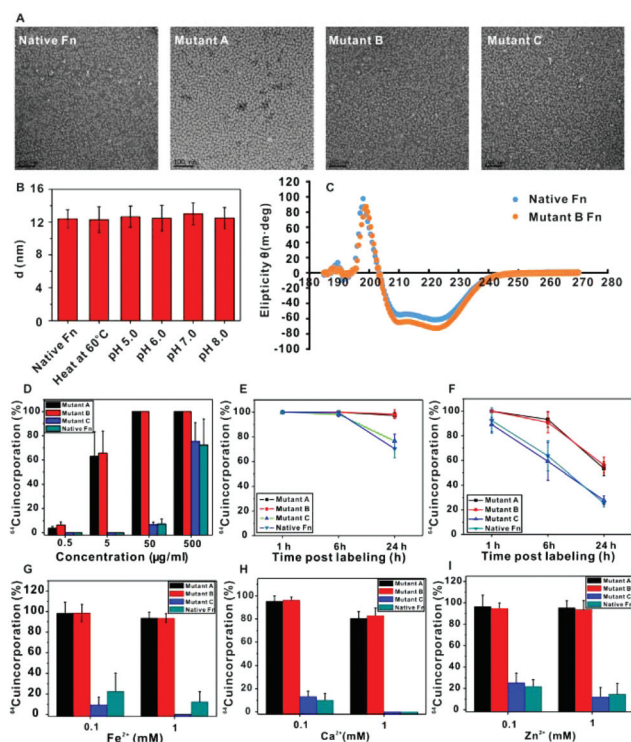

**Fig. 2** (A) TEM images of ferritin variants with uranyl acetate negative staining. Scale bar = 100 nm. (B) Dynamic light scattering study of the nanocage size of mutant B ferritin under heating (60 °C) and at different pH values in buffers. (C) Circular dichroism spectra of native ferritin and mutant B ferritin in PBS (0.5 mg mL<sup>-1</sup>). (D) Radioactive  $^{64}\text{Cu}$  incorporation ratio of ferritin variants under different concentrations. (E)  $^{64}\text{Cu}$  incorporation stability study of ferritin variants in mouse serum over 24 h. (F)  $^{64}\text{Cu}$  incorporation stability study of ferritin variants in the presence of a strong metal chelator, EDTA, in mouse serum over 24 h. (G–I) Divalent metal ion competition with  $^{64}\text{Cu}$  in ferritin variants.

We then investigated the coordination of  $\text{Cu}^{2+}$  with self-assembling protein analogues. The radioisotopic  $^{64}\text{Cu}^{2+}$  was used in our study to facilitate sensitive and quantitative read-outs over the subtle amino acid residue variations in protein analogues. The chelator, 2,2'-bipyridine, was firstly used to prepare metal ion free ferritin nanocages before adding  $^{64}\text{Cu}^{2+}$  into protein solutions. The incorporation of  $^{64}\text{Cu}^{2+}$  was over 65% at 5  $\mu\text{g mL}^{-1}$  of mutant A and B proteins, whereas the native ferritin had marginal  $^{64}\text{Cu}^{2+}$  binding capacity at the same protein concentration (Fig. 2D). Higher protein concentrations (50  $\mu\text{g mL}^{-1}$ ) led to over 95%  $^{64}\text{Cu}^{2+}$  incorporation for mutants A and B, while native ferritin showed less than 10%  $^{64}\text{Cu}^{2+}$  binding, presumably through the non-specific binding of  $^{64}\text{Cu}^{2+}$  with amino acid residues, such as histidine, and through the hydrophobic domains within the ferritin structure.<sup>37</sup> The stability test of  $^{64}\text{Cu}^{2+}$  coordinated ferritin derivatives in mouse serum demonstrated the high affinity of  $^{64}\text{Cu}^{2+}$  for mutants A and B over 24 h, whereas native ferritin and mutant control showed dramatic  $^{64}\text{Cu}^{2+}$  loss within the same time frame (Fig. 2E). Ethylenediaminetetraacetic acid (EDTA) has a fairly high stability constant to a number of divalent transition metal ions,<sup>38</sup> including  $\text{Cu}^{2+}$ . In our study, we discovered that the high affinity of  $^{64}\text{Cu}^{2+}$  for mutants A and B is able to resist competitive binding from EDTA for at least 6 h, and over 50%  $^{64}\text{Cu}^{2+}$  remained complexed after 24 h of co-incubation. In contrast, mutant C and native ferritin had dramatic loss of  $^{64}\text{Cu}^{2+}$  over the incubation period (Fig. 2E).


Next, we calculated the number of copper binding pockets of the ferritin derivatives. After incubation with  $^{64}\text{Cu}^{2+}$ , various concentrations of cold  $\text{Cu}^{2+}$  were added to the ferritin- $^{64}\text{Cu}^{2+}$  solution. The copper binding pocket numbers were calculated by the formula: ( $^{64}\text{Cu}^{2+}$ )  $\times$  Yield/Moles (Ferritin). Table S2† summarizes all experimental parameters and the calculated results. The mutant A has a maximum of 18 accessible  $\text{Cu}^{2+}$  binding pockets in the assembled protein nanocage, and mutant B has 20 copper binding pockets. The experimental results are highly consistent with the computational modeling calculation which predicts that mutant B possesses slightly larger interfacial areas and lower binding entropy in the presence of  $\text{Cu}^{2+}$  at the designed interface coordination domain (Fig. 1). In contrast, mutant C and native ferritin have limited  $\text{Cu}^{2+}$  binding capacities. To further confirm the highly specific binding of  $\text{Cu}^{2+}$  to the re-engineered mutants A and B over other divalent transition metals, a competitive binding assay was conducted. In the presence of 1 mM of cold divalent metal ions in solution, the  $^{64}\text{Cu}^{2+}$  incorporation ratio remained unchanged in mutants A and B, whereas mutant C and native ferritin had significant  $^{64}\text{Cu}^{2+}$  replacement with other divalent metals at 0.1 mM concentration.

## Cellular interaction of the interface re-engineered ferritin nanocage and cytotoxicity of DOX@mutant B

The improved physicochemical features of mutant B over the native ferritin and mutant A in terms of high structural stability and  $\text{Cu}^{2+}$  binding affinity make it an optimal nanoprobe for highly sensitive PET imaging. We thus used mutant B as a




quintessential example to investigate its interaction with cancer cells. It was reported that ferritins are highly favorable to interact with various cancer cells and enter into the cytosol through transferrin receptor mediated binding and internalization.<sup>14,29</sup> The confocal laser scanning microscopy (CLSM) imaging results showed that various cancer cells readily take up mutant B (labeled with Cy5.5 on the protein surface) into the cytoplasm after 4 h incubation (Fig. S6†). In our subsequent studies, we selected a malignant glioblastoma cell line, U87MG, as the cancer cell model for *in vitro* and *in vivo* studies. The CLSM imaging results indicated that mutant B and native ferritin had similar cellular uptake behavior (Fig. 3A). This is a critical indication that the interface re-engineering of subunits does not markedly alter surface properties of ferritin nanocages in their interaction with cancer cell surface receptors. The 3D CLSM imaging analysis showed that the mutant B was only distributed in the cytoplasm (Fig. 3B) with an extremely high uptake rate (>97%), independent of protein concentrations (Fig. 3C). The cytotoxicity of mutant B@DOX was further investigated *via* MTT assay. The mutant B@DOX was incubated with U87MG cells for 48 h, and free DOX was used as a control. As shown in Fig. 3D, the half maximal inhibitory concentration ( $IC_{50}$ ) of mutant B@DOX (0.44  $\mu$ M) is comparable to that of free DOX (0.37  $\mu$ M). Importantly, the mutant B nanocage alone shows no disturbance on cancer cell viability (Fig. 3D and S7†). These data verified that the mutant B@DOX can be used as a promising candidate for cancer therapy.

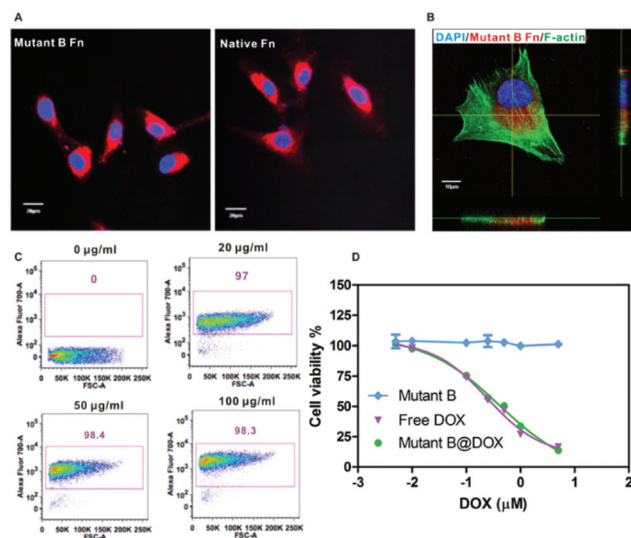

**Fig. 3** (A) Cancer cell (U87MG) uptake of ferritin variants labeled with the Cy5.5 fluorophore. Scale bar = 20  $\mu$ m. (B) Magnified confocal laser scanning imaging (CLSM) (Z-section) of the intracellular uptake of mutant B ferritin after 2 h incubation. Scale bar = 10  $\mu$ m. Blue: nucleus counterstained with DAPI; Red: Cy5.5 labeled mutant B ferritin; Green: F-actin stained with Alexa488 conjugated phalloidin. (C) Flow cytometry analysis of the cellular uptake of mutant B ferritin at different concentrations. (D) MTT assay of mutant B ferritin with cancer cells ( $n = 6$ ).

## **In vivo distribution of the interface re-engineered ferritin nanocage**

The pharmacokinetics (PK) and distribution of nanomaterials in living animals are two key factors determining their suitability as probes for molecular imaging or as delivery vehicles for effective drug delivery.<sup>39</sup> We investigated the biodistribution and blood circulation of the re-engineered ferritin nanocage (mutant B) in comparison with the native ferritin in healthy mice. Our results showed that mutant B had very similar PK and distribution behaviors as those of the native ferritin (Fig. 4A and B and Table 2), suggesting that the interface re-engineering strategy on the ferritin subunit retained the original surface properties of the self-assembled protein in the blood. Most nanomaterials rely heavily on surface modifi-

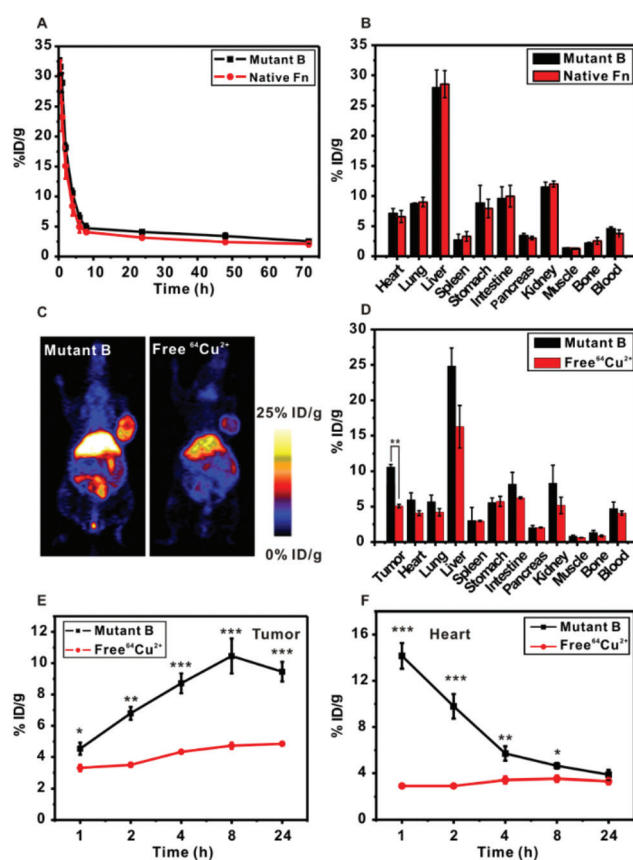

**Fig. 4** (A) Pharmacokinetics of  $^{64}\text{Cu}$  coordinated mutant B ferritin and native ferritin in healthy balb/c mice over 72 h ( $n = 3$  per group). (B) Biodistribution of  $^{64}\text{Cu}$  coordinated mutant B ferritin and native ferritin in different major organs in healthy balb/c mice at 24 h postinjection ( $n = 3$  per group). (C) PET images of  $^{64}\text{Cu}$  coordinated mutant B ferritin (left panel) and free  $^{64}\text{Cu}^{2+}$  (right panel) in U87MG tumor mice. (D) Biodistribution of  $^{64}\text{Cu}$  coordinated mutant B ferritin and free  $^{64}\text{Cu}^{2+}$  in U87MG tumor mice at 24 h postinjection ( $n = 3$  per group).  $^{**}P < 0.01$ . (E) Quantitative analysis of the tumor uptake of  $^{64}\text{Cu}$  coordinated mutant B ferritin and free  $^{64}\text{Cu}^{2+}$  at different time points ( $n = 3$  per group).  $^{*}P < 0.05$ ;  $^{**}P < 0.01$ ;  $^{***}P < 0.001$ . (F) Quantitative analysis of signals from the heart of  $^{64}\text{Cu}$  coordinated mutant B ferritin and free  $^{64}\text{Cu}^{2+}$  in U87MG tumor mice at different time points ( $n = 3$  per group).  $^{*}P < 0.05$ ;  $^{**}P < 0.01$ ;  $^{***}P < 0.001$ .

**Table 2** Pharmacokinetics of  $^{64}\text{Cu}$  coordinated mutant B and native ferritin nanoprobe in healthy balb/c mice ( $n = 3$  per group)


Group	AUC infusion (% ID mL $^{-1}$ h $^{-1}$ )	AUC 0.72 (% ID mL $^{-1}$ h $^{-1}$ )	CL (mL h $^{-1}$ )	T $_{1/2}$ (h)	V $_{SS}$ (mL)
Mutant	648.21328	367.30096	0.154315197	72.2	13.97749
WT	556.08956	292.65964	0.179831144	81.91	18.47092

cation with poly(ethylene glycol) (PEG) to prolong circulation and minimize macrophage uptake *in vivo*. For example, bacteriophage MS2 capsids underwent extensive external PEGylation to obtain long blood circulation times along with chemical modification of the capsid interior with chelators to allow for PET imaging.<sup>40</sup> The modification of protein cage interior and exterior surfaces fundamentally changes the surface properties of the original protein, and has the risk of compromised protein assembly integrity. On top of that, the intensive chemical modification usually requires additional purification steps, which seriously hampers the protein yield and quality. In sharp contrast, our re-engineering method avoids surface PEGylation, and retains the nanocage for comparable blood circulation time ( $t_{1/2} = 72$  h for mutant B) as that of the original ferritin. Meanwhile, the re-engineered protein nanocage (mutant B) stably sequesters  $^{64}\text{Cu}^{2+}$  within the structure for PET imaging.

It was found that free  $^{64}\text{Cu}^{2+}$  ions are likely to accumulate in the liver and bladder.<sup>40</sup> In our research, we found that free  $^{64}\text{Cu}^{2+}$  also has affinity to tumor associated tissues (Fig. 4C).<sup>41</sup> Nevertheless, the  $^{64}\text{Cu}^{2+}$  labeled re-engineered ferritin nanocage (mutant B) showed strikingly 2.5-fold higher tumor retention than the free  $^{64}\text{Cu}^{2+}$  after 8 h, and remained 2-fold higher after 24 h (Fig. 4C–E). In addition, the free  $^{64}\text{Cu}^{2+}$  remained at a constant level in the circulation, while the mutant B coordinated  $^{64}\text{Cu}^{2+}$  presented a typical fast elimination in the first 4 h, followed by a gradual excretion in the next 20 h (Fig. 4F). The mutant B coordinated  $^{64}\text{Cu}^{2+}$  and free  $^{64}\text{Cu}^{2+}$  demonstrate drastically different PK and distribution behavior. We conclude that the PET results from  $^{64}\text{Cu}^{2+}$  represent the nanoprobe behavior with minimal, if any, free  $^{64}\text{Cu}^{2+}$  interference. We have confirmed that the coordination of  $^{64}\text{Cu}^{2+}$  with mutant B is in a chemically stable status, the  $^{64}\text{Cu}^{2+}$  labeled re-engineered ferritin nanocage is thus a robust nanoprobe for PET imaging.

### PET imaging of tumor using the interface re-engineered ferritin nanoprobe

We used the human glioblastoma cell line, U87MG, as a tumor model to evaluate the new re-engineered ferritin nanoprobe. To inject an equivalent dose of radioactivity (150  $\mu\text{Ci}$ ), 20 times lower amount of the mutant B ferritin nanoprobe was needed relative to the native ferritin. The lower protein usage would minimize the immunogenicity and avoid non-specific distribution in animals. Interestingly,  $^{64}\text{Cu}^{2+}$  labeled mutant B resulted in consistently higher tumor uptake than that of native ferritin over 24 h (Fig. 5A). Quantitative analysis indicated that the interface re-engineered mutant B nanoprobe

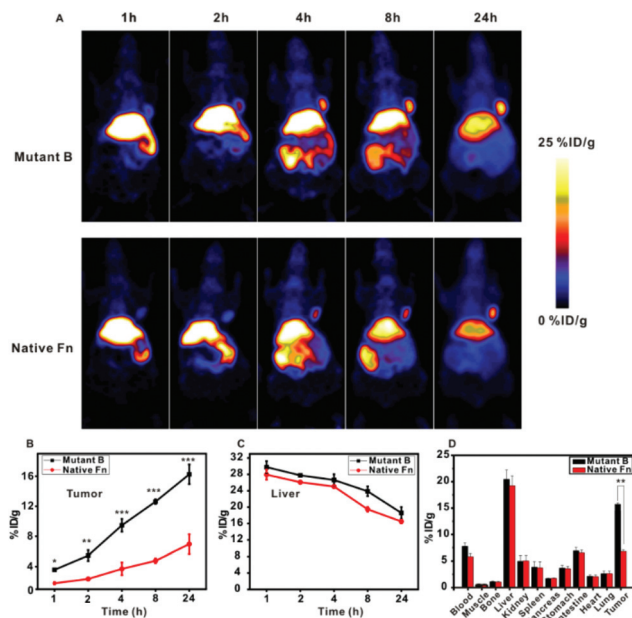

**Fig. 5** (A) PET imaging of  $^{64}\text{Cu}$  coordinated mutant B ferritin (upper panel) and native ferritin (lower panel) of U87MG tumor mice at different time points. An equivalent of 150  $\mu\text{Ci}$  radioactivity was injected into each mouse. (B) Quantitative analysis of the tumor accumulation of  $^{64}\text{Cu}$  coordinated mutant B and native ferritin nanoprobe at different time points ( $n = 3$  per group). (C) Quantitative analysis of the liver retention of  $^{64}\text{Cu}$  coordinated mutant B and native ferritin nanoprobe at different time points ( $n = 3$  per group). (D) Biodistribution of  $^{64}\text{Cu}$  coordinated mutant B and native ferritin nanoprobe at 24 h postinjection ( $n = 3$  per group).  $^{**}P < 0.05$ .

had 16% ID  $\text{g}^{-1}$  at the tumor site after 24 h, while the native ferritin had only 5% ID  $\text{g}^{-1}$  in the same time frame (Fig. 5B). It is also of note that the observed 5% ID  $\text{g}^{-1}$  tumor site radioactivity could be attributed collectively to the released free  $^{64}\text{Cu}^{2+}$  from the native ferritin nanocage and the loosely incorporated  $^{64}\text{Cu}^{2+}$  within the native ferritin. This possible heterogeneity incorporating free  $^{64}\text{Cu}^{2+}$  and coordinated  $^{64}\text{Cu}^{2+}$  makes it difficult for data interpretation. Meanwhile, the liver uptakes of  $^{64}\text{Cu}^{2+}$  are almost identical in permuted and native ferritins (Fig. 5C). Therefore, the highly specific tumor accumulation in PET imaging was obtained by the re-engineered mutant B nanoprobe (Fig. 5).

### Investigation of tumor treatment by mutant B@DOX *in vivo*


Encouraged by the promising MTT result *in vitro*, the antitumor ability of mutant B@DOX was further investigated in a U87MG xenograft tumor model *in vivo*. When the volume of

the tumor reached 80 mm<sup>3</sup>, the tumor-bearing nude mice were divided into five groups randomly with the following treatment: mutant B@DOX (12.5 mg kg<sup>-1</sup> of mutant B and 2 mg kg<sup>-1</sup> of DOX), free DOX (2 mg kg<sup>-1</sup>), DOXIL® (2 mg kg<sup>-1</sup>), mutant B (12.5 mg kg<sup>-1</sup>), and saline injection every other day three times. As shown in Fig. 6A, both mutant B@DOX and DOXIL® groups were more efficacious than all the other groups. Interestingly, the mutant B@DOX group exhibited the best tumor inhibition, which may be due to the prolonged circulation time of mutant B in the blood (Fig. 5). Moreover, the mutant B@DOX can promote the tumor mice survival rate (Fig. 6B), and no mice died after 50 days. Conversely, all mice died within 28 days in the control group. The body weight was also measured from various groups. There was no obvious body weight loss during the whole period of experiments in the mutant B@DOX group (Fig. 6C). The body weight of animals treated with DOXIL® and free DOX decreased slightly. In addition, hematoxylin–eosin (H&E) stained images of major organs are shown in Fig. S9.† Compared to the control group, all the treatment groups showed no obvious systemic toxicity. The H&E stained images of tumor sections from different groups are shown in Fig. 6D. Compared to all the other groups, greater tumor cell apoptosis and necrosis can be detected after the administration of mutant B@DOX. The above results demonstrated that the mutant B@DOX can

suppress tumor growth effectively and prolong survival time of tumor bearing mice.

## Conclusion

There have been prodigious efforts to control the self-assembly behavior of proteins to design advanced protein architectures, or incorporate novel functions for various applications. The combination of divalent transition metal coordination with interface re-engineered mutant protein assembling subunits provides a simple and robust strategy to diversify the original protein structures. Importantly, the interface re-engineering approach simultaneously strengthens the structural stability of the protein ensemble, lowers the interfacial entropy, and expands its function. The widely used self-assembled ferritin nanocage coordinated with a divalent transition metal ion, copper, was used as a prototypical example to demonstrate the advantages of the interface re-engineering strategy to enhance self-assembly protein stability and biofunctionality. Moreover, the copper ion can promote the DOX loading efficiency in the mutant ferritin. The as-prepared theranostic nanoplateform enhanced specific PET imaging of tumor and inhibited the tumor growth efficiently. We envision that this one-step labeling and DOX encapsulated re-engineering ferritin will provide

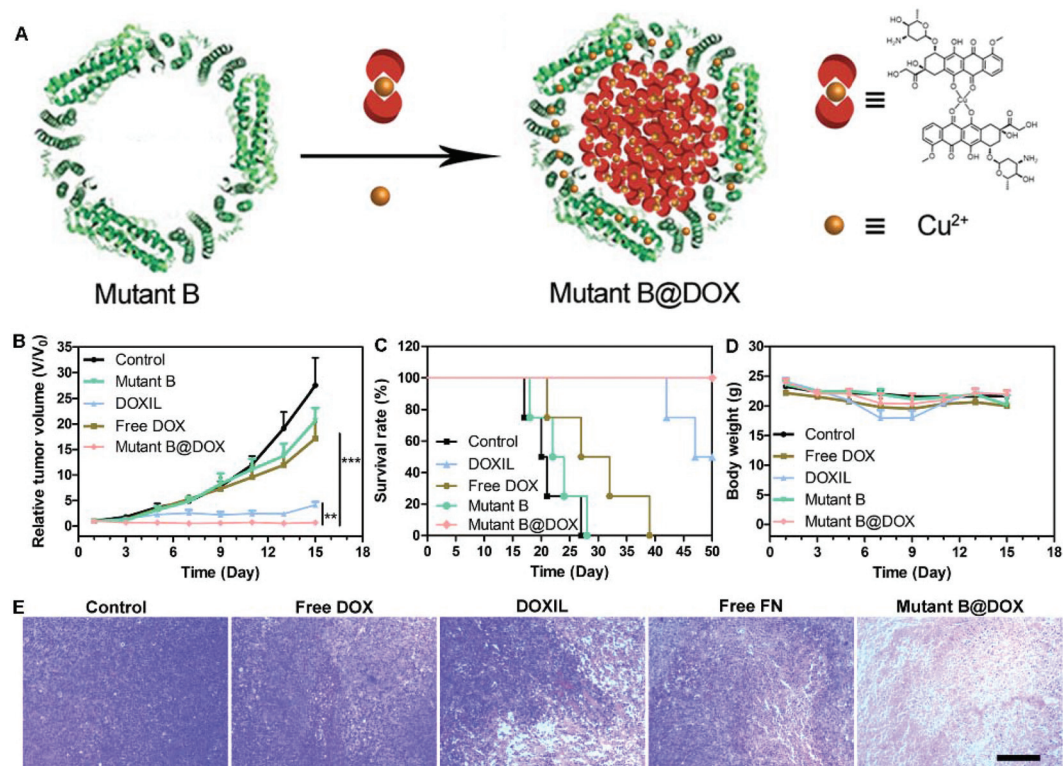

**Fig. 6** (A) Schematic illustration of mutant B@DOX preparation. Cu<sup>2+</sup> was coordinated with DOX first, then the DOX-Cu<sup>2+</sup> complexes were encapsulated into the mutant B ferritin. (B) Tumor growth curves under various treatments. (C) Survival rates of tumor xenograft mice from different groups. (D) The body weight of mice from different groups. (E) H&E stained tumor histological sections from different groups on the 7<sup>th</sup> day. Scale bar = 200 μm. \*\**P* < 0.05, \*\*\**P* < 0.01.



a new approach to engineer existing proteins for nanomedicine applications.

## Materials and methods

### Reagents

All chemical reagents were purchased from Sigma-Aldrich. Primers were purchased from Integrated DNA Technologies. Deionized (DI) water with a resistivity of 18.0 MΩ was obtained from a Millipore water purification system.

### Cell lines

HT29, SKOV3, U87MG, A549, PC3, and MDA-MB-231 cell lines were purchased from the American Type Culture Collection (ATCC, Rockville, MD, USA) and cultured in different media with 10% FBS (HT29 and SKOV3 cells were cultured in McCoy's 5A media, U87MG and A549 cells were cultured in MEM media, PC3 cells were cultured in F-12 media, and MDA-MB-231 cells were cultured in L-15 media). BL21 (DE3) competent cells were bought from Thermo Fisher Scientific.

### Experimental procedures

**Preparation of ferritin and ferritin mutants.** Specific amino acid mutation sites were introduced in a ferritin coding sequence. A total of three ferritin mutants were prepared. All the ferritin and ferritin mutants were expressed in a vector with a backbone of pRSFDuet-1. The construction of ferritin mutants was performed according to a step by step polymerase chain reaction (PCR) synthetic method. A total of 10 primers were used for mutant preparation (see the ESI† for primer details).

After five rounds of PCR, ferritin coding sequences were inserted into the vectors by NcoI and XhoI double digestion. After confirmation by sequencing, ferritin mutant plasmids were transformed into BL21 (DE3) cells. For ferritin expression, 1 L LB medium containing ferritin *E. coli* was grown at 37 °C until OD<sub>600</sub> 0.6 was attained, followed by induction with 1 mM IPTG at 37 °C for 4 h. Bacteria were collected by centrifugation at 7000g for 10 min, followed by sonication in PBS. The supernatant was collected after centrifugation at 13 000g for 10 min, and then incubated at 60 °C with a water bath for 10 min. After centrifugation at 13 000g for 10 min, the supernatant was purified using a HiLoad Superdex 200 PG (GE) column. The eluted proteins were used without further purification.

**Characterization of ferritin and ferritin mutants.** Transmission electron microscopy (TEM) images were obtained on a FEI Tecnai 12 (120 kV) transmission electron microscope. For TEM analysis, samples were prepared by coating a 20 µL protein solution onto carbon coated copper grids, followed by 20 µL uranyl acetate (1%) negative staining.

**Preparation of ferritin and ferritin mutants for metal ion binding.** Ferritins used for metal ion binding were dialyzed into sodium acetate (50 mM pH 5.0) first. Then, 5 mM sodium dithionite and 1 mM 2,2'-bipyridine were added to the ferritin solution to facilitate iron removal. After final dialysis into sodium acetate (50 mM pH 5.0), the proteins were ready for use.

**Cytotoxicity assay.** Different cell lines (HT29, U87MG, NIH3T3, PC3 and HEK293) were used in the cytotoxicity assay. Cells were seeded in 96 well plates at a density of  $1 \times 10^4$  cells per well and cultured in their appropriate media. 24 h later, different concentrations of ferritins (1, 10, 50, 80 and 100 µg mL<sup>-1</sup>) were added into each well and incubated at 37 °C for 24 h. After washing with PBS, 5 µ MTT (10 µg mL<sup>-1</sup>) solution was added into each well and incubated for another 3 h. 100 µL DMSO was added into each well to dissolve the intracellular formazan crystals. A plate reader was used to measure the absorbance at 570 nm.

**DOX loading procedure in mutant B.** DOX (400 µL, 1 mg mL<sup>-1</sup>) was incubated with CuCl<sub>2</sub> (10 mg mL<sup>-1</sup>) for 2 h, and then mutant B (1 mL, 2 mg mL<sup>-1</sup>) was added into the above solution for another 6 h. Next, the mutant B@DOX was purified by using an Amersham Biosciences PD-10 desalting column to remove the free DOX and Cu<sup>2+</sup>. The content of DOX was quantified by HPLC at a wavelength of 480 nm. The DOX loading content was calculated by the formula: loading content (%) = DOX/(DOX + mutant B) × 100. The DOX encapsulation efficiency is 6.9%, and the DOX loading content is 13.8%.

**Animal models.** All animal studies involved in this project were conducted according to a protocol approved by the National Institutes of Health Animal Care and Use Committee (NIH-ACUC). 6–7-week-old athymic nude mice purchased from Harlan were subcutaneously injected with  $2 \times 10^6$  human glioblastoma U87MG cells on the right flank. The animals were ready for PET imaging studies and tumor therapy experiments when the tumor size reached about 200 and 80 mm<sup>3</sup>, respectively.

**<sup>64</sup>Cu<sup>2+</sup> binding study.** <sup>64</sup>Cu<sup>2+</sup> (500 µCi) was added into different concentrations of ferritins (0.5, 5, 50 and 500 µg mL<sup>-1</sup>) to evaluate the binding ability of ferritin and ferritin mutants. After 1 h of incubation, instant thin layer chromatography (iTLC) was used to evaluate the labeling efficiency of different ferritins.

**Metal ion competition study.** After 1 h incubation of <sup>64</sup>Cu<sup>2+</sup> (500 µCi) and ferritins, different metals (Ca<sup>2+</sup>, Fe<sup>2+</sup> and Zn<sup>2+</sup>) of different concentrations (0.1 and 1 mM) were added into ferritin solutions (1 mg mL<sup>-1</sup>). iTLC was used to test the binding between <sup>64</sup>Cu<sup>2+</sup> and ferritins.

**MicroPET imaging.** U87MG tumor bearing mice were injected intravenously with ferritins (10 µg for native ferritin and 0.5 µg for mutant B) and 150 µCi <sup>64</sup>Cu<sup>2+</sup>. PET scanning and imaging analysis were performed on a micro PET scanner (Siemens Inveon) at 1, 2, 4, 8, and 24 h post injection. 3-Dimensional regions of interest (ROIs) were drawn on the organs and tumors with decay-corrected whole body coronal images. The percentage injected dose per gram (% ID g<sup>-1</sup>) was then calculated according to the ROI readings.

**Biodistribution.** Mice were sacrificed after the 24 h PET scanning. Organs of interest and tumors were collected and weighed. The radioactivity was measured with a gamma counter (Beckman 8000). The uptake of <sup>64</sup>Cu was calculated in % ID g<sup>-1</sup> according to the prepared standards.



**Pharmacokinetics study.** A 300  $\mu\text{Ci}$   $^{64}\text{Cu}^{2+}$ -ferritin complex was injected into mice through the tail vein. Mice blood samples were collected at different time points (0.5, 1, 2, 4, 6, 8, 24, 48 and 72 h) after injection. Blood samples were weighed and radioactivity was measured with a gamma counter. The % ID  $\text{g}^{-1}$  was also calculated for comparison.

**Tumor therapy study.** The U87MG tumor-bearing mice were divided into five groups. The *in vivo* treatment studies were performed by tail vein injection with PBS, DOX (2  $\text{mg kg}^{-1}$ ), Doxil® (2  $\text{mg kg}^{-1}$ ), mutant B (12.5  $\text{mg kg}^{-1}$ ), and mutant B@DOX (12.5  $\text{mg kg}^{-1}$  of mutant B and 2  $\text{mg kg}^{-1}$  of DOX) every other day three times. The body weight and tumor size were monitored every other day. The tumor volumes were calculated by the formula:  $V = \text{length (mm)} \times \text{width (mm)}^2/2$ .

## Conflicts of interest

The authors declare no competing financial interest.

## Acknowledgements

This work was supported by the Major State Basic Research Development Program of China (2017YFA0205201, 2014CB744503, and 2013CB733802), the National Natural Science Foundation of China (NSFC) (81422023, 51273165, 81371596, and U1505221), the intramural research program (IRP), and the National Institutes of Health (NIH).

## References

- 1 A. Fegan, B. White, J. C. Carlson and C. R. Wagner, *Chem. Rev.*, 2010, **110**, 3315–3336.
- 2 S. Jones and J. M. Thornton, *Proc. Natl. Acad. Sci. U. S. A.*, 1996, **93**, 13–20.
- 3 Z. Wang, F. Zhang, Z. Wang, Y. Liu, X. Fu, A. Jin, B. C. Yung, W. Chen, J. Fan, X. Yang, G. Niu and X. Chen, *J. Am. Chem. Soc.*, 2016, **138**, 15027–15034.
- 4 Y. Hsia, J. B. Bale, S. Gonen, D. Shi, W. Sheffler, K. K. Fong, U. Nattermann, C. Xu, P. S. Huang, R. Ravichandran, S. Yi, T. N. Davis, T. Gonen, N. P. King and D. Baker, *Nature*, 2016, **535**, 136–139.
- 5 R. Zandi, D. Reguera, R. F. Bruinsma, W. M. Gelbart and J. Rudnick, *Proc. Natl. Acad. Sci. U. S. A.*, 2004, **101**, 15556–15560.
- 6 S. Abe, K. Hirata, T. Ueno, K. Morino, N. Shimizu, M. Yamamoto, M. Takata, E. Yashima and Y. Watanabe, *J. Am. Chem. Soc.*, 2009, **131**, 6958–6960.
- 7 M. Uchida, M. L. Flenniken, M. Allen, D. A. Willits, B. E. Crowley, S. Brumfield, A. F. Willis, L. Jackiw, M. Jutila, M. J. Young and T. Douglas, *J. Am. Chem. Soc.*, 2006, **128**, 16626–16633.
- 8 M. Comellas-Aragones, H. Engelkamp, V. I. Claessen, N. A. Sommerdijk, A. E. Rowan, P. C. Christianen, J. C. Maan, B. J. Verduin, J. J. Cornelissen and R. J. Nolte, *Nat. Nanotechnol.*, 2007, **2**, 635–639.
- 9 Z. Wang, P. Huang, O. Jacobson, Z. Wang, Y. Liu, L. Lin, J. Lin, N. Lu, H. Zhang, R. Tian, G. Niu, G. Liu and X. Chen, *ACS Nano*, 2016, **10**, 3453–3460.
- 10 X. Lin, J. Xie, L. Zhu, S. Lee, G. Niu, Y. Ma, K. Kim and X. Chen, *Angew. Chem., Int. Ed.*, 2011, **50**, 1569–1572.
- 11 J. M. Fletcher, R. L. Harniman, F. R. Barnes, A. L. Boyle, A. Collins, J. Mantell, T. H. Sharp, M. Antognozzi, P. J. Booth, N. Linden, M. J. Miles, R. B. Sessions, P. Verkade and D. N. Woolfson, *Science*, 2013, **340**, 595–599.
- 12 B. Worsdorfer, K. J. Woycechowsky and D. Hilvert, *Science*, 2011, **331**, 589–592.
- 13 M. Liang, K. Fan, M. Zhou, D. Duan, J. Zheng, D. Yang, J. Feng and X. Yan, *Proc. Natl. Acad. Sci. U. S. A.*, 2014, **111**, 14900–14905.
- 14 K. Fan, C. Cao, Y. Pan, D. Lu, D. Yang, J. Feng, L. Song, M. Liang and X. Yan, *Nat. Nanotechnol.*, 2012, **7**, 459–464.
- 15 M. Uchida, H. Kosuge, M. Terashima, D. A. Willits, L. O. Liepold, M. J. Young, M. V. McConnell and T. Douglas, *ACS Nano*, 2011, **5**, 2493–2502.
- 16 K. S. Raja, Q. Wang, M. J. Gonzalez, M. Manchester, J. E. Johnson and M. G. Finn, *Biomacromolecules*, 2003, **4**, 472–476.
- 17 Y. S. Nam, H. Park, A. P. Magyar, D. S. Yun, T. S. Pollom Jr. and A. M. Belcher, *Nanoscale*, 2012, **4**, 3405–3409.
- 18 B. Maity, K. Fujita and T. Ueno, *Curr. Opin. Chem. Biol.*, 2015, **25**, 88–97.
- 19 D. J. Huard, K. M. Kane and F. A. Tezcan, *Nat. Chem. Biol.*, 2013, **9**, 169–176.
- 20 M. Dalmau, S. Lim and S. W. Wang, *Nano Lett.*, 2009, **9**, 160–166.
- 21 E. N. Salgado, J. D. Brodin, M. M. To and F. A. Tezcan, *Inorg. Chem.*, 2011, **50**, 6323–6329.
- 22 E. N. Salgado, R. A. Lewis, J. Faraone-Mennella and F. A. Tezcan, *J. Am. Chem. Soc.*, 2008, **130**, 6082–6084.
- 23 C. M. Summa, M. M. Rosenblatt, J.-K. Hong, J. D. Lear and W. F. DeGrado, *J. Mol. Biol.*, 2002, **321**, 923–938.
- 24 Y. T. Lai, E. Reading, G. L. Hura, K. L. Tsai, A. Laganowsky, F. J. Asturias, J. A. Tainer, C. V. Robinson and T. O. Yeates, *Nat. Chem.*, 2014, **6**, 1065–1071.
- 25 R. A. Jockusch, A. S. Lemoff and E. R. Williams, *J. Am. Chem. Soc.*, 2001, **123**, 12255–12265.
- 26 Z. Zhen, W. Tang, H. Chen, X. Lin, T. Todd, G. Wang, T. Cowger, X. Chen and J. Xie, *ACS Nano*, 2013, **7**, 4830–4837.
- 27 X. Cai, Y. Luo, W. Zhang, D. Du and Y. Lin, *ACS Appl. Mater. Interfaces*, 2016, **8**, 22442–22450.
- 28 A. Jabłońska-Trypuć, G. Świdorski, R. Krętowski and W. Lewandowski, *Molecules*, 2017, **22**, 1106.
- 29 L. Li, C. J. Fang, J. C. Ryan, E. C. Niemi, J. A. Lebron, P. J. Bjorkman, H. Arase, F. M. Torti, S. V. Torti, M. C. Nakamura and W. E. Seaman, *Proc. Natl. Acad. Sci. U. S. A.*, 2010, **107**, 3505–3510.

- 30 Y. Zhao, M. Liang, X. Li, K. Fan, J. Xiao, Y. Li, H. Shi, F. Wang, H. S. Choi, D. Cheng and X. Yan, *ACS Nano*, 2016, **10**, 4184–4191.
- 31 E. J. Lee, K. Y. Ahn, J. H. Lee, J. S. Park, J. A. Song, S. J. Sim, E. B. Lee, Y. J. Cha and J. Lee, *Adv. Mater.*, 2012, **24**, 4739–4744.
- 32 D. M. Lawson, P. J. Artymiuik, S. J. Yewdall, J. M. Smith, J. C. Livingstone, A. Treffry, A. Luzzago, S. Levi, P. Arosio, G. Cesareni, *et al.*, *Nature*, 1991, **349**, 541–544.
- 33 E. N. Salgado, R. A. Lewis, S. Mossin, A. L. Rheingold and F. A. Tezcan, *Inorg. Chem.*, 2009, **48**, 2726–2728.
- 34 Y. Zhang and B. P. Orner, *Int. J. Mol. Sci.*, 2011, **12**, 5406–5421.
- 35 M. Kanekiyo, C. J. Wei, H. M. Yassine, P. M. McTamney, J. C. Boyington, J. R. Whittle, S. S. Rao, W. P. Kong, L. Wang and G. J. Nabel, *Nature*, 2013, **499**, 102–106.
- 36 Z. Ke, S. Abe, T. Ueno and K. Morokuma, *J. Am. Chem. Soc.*, 2012, **134**, 15418–15429.
- 37 D. Boyd, C. Vecoli, D. M. Belcher, S. K. Jain and J. W. Drysdale, *J. Biol. Chem.*, 1985, **260**, 11755–11761.
- 38 S. Boija, A. Almesaker, E. Hedenstrom, D. Bylund, H. Edlund and M. Norgren, *J. Mass Spectrom.*, 2014, **49**, 550–556.
- 39 Z. Wang, G. Niu and X. Chen, *Pharm. Res.*, 2014, **31**, 1358–1376.
- 40 M. E. Farkas, I. L. Aanei, C. R. Behrens, G. J. Tong, S. T. Murphy, J. P. O'Neil and M. B. Francis, *Mol. Pharm.*, 2013, **10**, 69–76.
- 41 W. Guo, X. Sun, O. Jacobson, X. Yan, K. Min, A. Srivatsan, G. Niu, D. O. Kiesewetter, J. Chang and X. Chen, *ACS Nano*, 2015, **9**, 488–495.